

Effect of yttrium-stabilized bismuth

by Dedi Karni


Submission date: 06-Feb-2021 09:52PM (UTC-0800)

Submission ID: 1503418554

File name: rium-stabilized_bismuth_bilayer_electrolyte_thickness_on_the.pdf (5.05M)

Word count: 6954

Character count: 37154



Effect of yttrium-stabilized bismuth bilayer electrolyte thickness on the electrochemical performance of anode-supported solid oxide fuel cells

Dedikarni Panuh^{a,b,1}, S.A. Muhammed Ali^{c,1}, Dody Yulianto^b,
Muhammad Fadhlullah Shukur^d, Andanastuti Muchtar^{a,c,*}

^a Department of Mechanical and Manufacturing Engineering, Faculty of Engineering and Built Environment, Universiti Kebangsaan Malaysia, 43600, UKM Bangi, Selangor, Malaysia

^b Department of Mechanical Engineering, Faculty of Engineering, Universitas Islam Riau, Indonesia

^c Fuel Cell Institute, Universiti Kebangsaan Malaysia, 43600, UKM Bangi, Selangor, Malaysia

^d Fundamental and Applied Sciences Department, Universiti Teknologi Petronas, 32610, Seri Iskandar, Malaysia

ARTICLE INFO

Keywords:

Bilayer electrolyte
Solid oxide fuel cell
Yttrium stabilized bismuth
Dip-coating

ABSTRACT

Lowering operating temperature and optimizing electrolyte thickness, while maintaining the same high efficiencies are the main considerations in fabricating solid oxide fuel cells (SOFCs). In this study, the effect of yttrium-stabilized bismuth bilayer electrolyte thickness on the electrical performance was investigated. The yttrium-stabilized bismuth bilayer electrolyte was coated on the nickel–samarium-doped composite anode/samarium-doped ceria electrolyte substrate with varying bilayer electrolyte thicknesses (1.5, 3.5, 5.5, and 7.5 μm) via dip-coating technique. Electrochemical performance analysis revealed that the bilayer electrolyte with 5.5 μm thickness exhibited high open circuit voltage, current and power densities of 1.068 V, 259.5 mA/cm² and 86 mW/cm², respectively at 600 °C. Moreover, electrochemical impedance spectroscopy analysis also exhibited low total polarization resistance (4.64 Ωcm²) at 600 °C for the single SOFC with 5.5 μm thick yttrium-stabilized bismuth bilayer electrolyte. These findings confirm that the yttrium-stabilized bismuth bilayer electrolyte contributes to oxygen reduction reaction and successfully blocks electronic conduction in Sm_{0.2}Ce_{0.8}O_{1.9} electrolyte materials. This study has successfully produced an Y_{0.25}Bi_{0.75}O_{1.5}/Sm_{0.2}Ce_{0.8}O_{1.9} bilayer system with an extremely low total polarization resistance for low-temperature SOFCs.

28

1. Introduction

The solid oxide fuel cell (SOFC) is the most promising electrochemical conversion devices for producing electricity from environment-friendly energy sources [1]. SOFCs typically operate at high temperatures between 700 °C and 1000 °C to achieve high efficiency [2]. However, high operating temperatures cause severe thermo-mechanical-chemical instability among components and act as a main barrier for the large-scale adoption of SOFCs technologies [3,4]. Most studies have focused on the development of intermediate-to low-temperature SOFCs operating at 500 °C–600 °C to expand the application of SOFCs [5,6]. Researchers have mainly focused on the development of new materials or adopted nanostructured architecture

and cost-effective processes to achieve highly efficient SOFC technology operating at temperatures between 500 °C and 700 °C [7,8]. However, reducing operating temperature can induce poor catalytic activity towards oxygen reduction reaction (ORR) rates at the cathode side and diminish ionic conductivity at the electrolyte, which affects the overall electrochemical performance of the SOFC cells [9–12]. The electrocatalytic activity toward the ORR (O₂ + 4H⁺ + 4e⁻ → 2H₂O) requires four proton-electron transfers to improve its rate-determining process/efficiency at the cathode side, especially at the reduced operating temperature [13,14]. Therefore, high catalytic activity towards ORR and ionic conductivity at the cathode and electrolyte sides are required to increase efficiency at a low-temperature operation, respectively [15]. Typically, lanthanum strontium manganite (LSM) or lanthanum

* Corresponding author. Department of Mechanical and Manufacturing Engineering, Faculty of Engineering and Built Environment, Universiti Kebangsaan Malaysia, 43600, UKM Bangi, Selangor, Malaysia.

E-mail addresses: dedikarni@eng.uir.ac.id (D. Panuh), mas@ukm.edu.my (S.A. Muhammed Ali), dody_yulianto@eng.uir.ac.id (D. Yulianto), mfadhlullah.ashukur@utp.edu.my (M.F. Shukur), muchtar@ukm.edu.my (A. Muchtar).

¹ Equally contributed.

<https://doi.org/10.1016/j.ceramint.2020.10.209>

Received 9 September 2020; Received in revised form 20 October 2020; Accepted 28 October 2020

Available online 4 November 2020

0272-8842/© 2020 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

strontium cobalt ferrite perovskite, yttrium-stabilized zirconia (YSZ), and nickel/YSZ (Ni/YSZ) cermet are the most investigated cathode, electrolyte, and anode materials for high-temperature SOFCs (HT-SOFC), respectively [16].

A conventional YSZ electrolyte material possess high ionic conductivity of 0.1 S/cm at 1000 °C; however its high operating temperature limits its application and also raises the overall cost of the cell [17]. Several studies have been conducted to develop highly conductive solid electrolyte, among which, aliovalent-doped ceria (CeO₂) and isovalent-cation-stabilized bismuth (Bi₂O₃) oxide are especially desirable due to their superior ionic conductivity at low temperatures [1]. For example, bismuth based electrolyte materials such as erbium stabilized bismuth (ESB) [18], yttrium stabilized bismuth (YSB) [19] and co-doped Dy–Gd stabilized bismuth and Dy–Ce stabilized bismuth oxide [20] have been considered promising solid electrolyte materials due to their high conductivity. All these dopants can stabilize bismuth oxide in cubic structures. Among these compositions, YSB exhibits higher ionic conductivity and lower ohmic resistance at the intermediate and low temperature compared with zirconia-based electrolyte materials [21,22]. Despite high conductivity of YSB, it was not commonly used in SOFCs due to its low thermodynamic stability [23]. This is because Bi₂O₃ electrolyte materials tend to decompose to form metallic bismuth at the reducing environment (H₂ and CH₄) [24]. Therefore, YSB electrolyte can be used at the electrolyte facing the anode side.

Samarium doped ceria (SDC) or gadolinium-doped ceria (GDC) electrolyte materials has received greater attention for the development of intermediate to low temperature SOFC due to its excellent ionic conductivity and phase stability at low-oxygen partial pressure (PO₂) [25]. However, CeO₂ electrolytes demonstrate mixed ionic-electronic conductive behaviour at low PO₂ (<10⁻¹⁴ atm), exhibiting significant n-type electronic conduction through the electrolyte [26]. In addition, the partial reduction of Ce⁴⁺ to Ce³⁺ contributes to the current leakage, further triggering electronic conduction (>600 °C), resulting in a sudden decline in open circuit voltage (OCV) and low mechanical strength at the reducing environment (anode side) [27,28]. These phenomenon decreases the ionic transference number of the SDC electrolyte; thereby reducing the efficiency of the SOFCs [24]. Therefore, to limit electrical induction during the application of SOFCs, it is important to enhance the stability and electrolytic domain of these materials. Efforts have focused on blocking electronic conduction by coating a barrier layer on the doped ceria electrolyte side facing the fuel side or the anode side as a means to improve the OCVs and mechanical stability.

The use of bilayer electrolytes is considered to be a simple but effective way of improving the thermodynamic stability of YSB and SDC electrolytes [29]. However, in several of these investigations, zirconia-based YSZ scandia-stabilized zirconia (ScSZ) electrolyte materials have been used to protect these high conductive materials from decomposition by preventing exposure to reducing environment (anode side) [17,30,31]. This is because zirconia-based electrolytes have demonstrated excellent mechanical and chemical stability in the reducing environment have also been commonly used as barrier layers for doped ceria electrolyte materials. Heidari et al. [32] reported that the performance of SDC electrolyte-based single SOFCs can be improved using YSZ bilayer electrolyte films and achieve higher OCVs at all operating temperatures. Other electronic current blocking materials were also investigated by researchers for ceria electrolyte [33]. In contrast, our paper consists of SDC on the anode side and YSB on the cathode side. This is because the YSB electrolyte layer on the cathode (air) side is expected to obstruct the electronic flow through the SDC layer due to its high transference number (ratio of ionic to total conductivity) [23,34]. The use of SDC and YSB electrolyte materials together often has several benefits, i.e. the presence of SDC layer on the anode side prevents the YSB layer from decomposition in the reducing environment (fuel gases), while the presence of YSB layers blocks electrical leakage through the SDC layer, resulting in high power density and enhanced mechanical stability [35]. A number of studies have

demonstrated that OCVs close to 1.0 V can be achieved with ceria/bismuth bilayer as electrolyte at the temperature range of 500–800 °C [36–39]. However, the relative thickness and transport properties of bilayers have a considerable effect on interfacial partial oxygen pressure, which can lead to the electrochemical instability of bilayer electrolyte SOFCs [24]. The decomposition of YSB bilayers can substantially decay the conductivity and increase the ohmic and area-specific resistance of SOFC cells, further resulting in powder density degradation. Optimizing the thickness of the bilayer electrolyte layer is necessary to increase the stability of the SDC electrolytes [40,41]. Mio et al. [40] studied the effect of ESB bilayer thickness on fuel cell performance and found that power density can increase from 84 to 249 mW/cm² when the bilayer electrolyte thickness is increased correspondingly from 13 to 20 μm at 500 °C; their study concluded that thin electrolyte layers are highly susceptible to fuel gas erosion.

Advanced deposition techniques based on ceramic powder processing have been used to improve the chemical and physical properties of bilayer electrolyte layers on dense electrolyte substrates [32,42,43]. These methods are well established, but the investment costs for their respective apparatus is higher than that for dip coating [9]. Dip coating is simple, inexpensive and satisfactory method to fabricate thin to thick YSB electrolyte films on SDC electrolytes because the thickness can be easily controlled on the basis of the number of dip coatings [32,44]. In this work, we fabricated the YSB bilayer electrolyte via a simple dip coating process on the uniaxially pressed NiO–SDC/SDC substrate. The present study aims to determine the effect of bilayer thickness (1.5, 3.5, 5.5, and 7.5 μm) on the interfacial polarization resistance and overall performance of bilayer electrolyte cells. An anode-supported single-cell SOFC, with SDC as the electrolyte, YSB as the bilayer electrolyte, Ag–YSB composite as the cathode, and NiO–SDC as the anode, was utilized for this purpose.

2. Experimental procedure

2.1. Powder synthesis and cell fabrication of anode-supported single SOFC

Yttrium oxide (99.999 wt%, Sigma Aldrich Sdn. Bhd), and bismuth (III) oxide (99.999 wt%, Sigma Aldrich Sdn. Bhd) were mixed together in ethanol to prepare YSB bilayer electrolyte via high-speed ball-milling [44]. The SDC (Ce_{0.8}Sm_{0.2}O_{1.9}) electrolyte powder was prepared via sol-gel method [45]. All of the reagents were purchased from Sigma Aldrich, Malaysia, with 99.8% purity. Stoichiometric amounts of Sm(NO₃)₃·6H₂O and Ce(NO₃)₃·6H₂O were dissolved together in deionized water and then citric acid (99.8%, Merck Chemicals, Germany) was slowly added to the mixture under continuous stirring. The molar ratio of the total metal ion: citric acid was 1:1.2. The solution mixture was stirred at 80 °C for 12 h to form a viscous gel. The gel was heated continuously to initiate combustion reaction and subsequently a pale yellow colored ash was obtained. The resulting ash was calcined at 850 °C for 5 h to obtain the desired SDC powder. The NiO–SDC composite anode powder was prepared by mixing nickel (II) oxide (99.8%, Sigma Aldrich, Malaysia) with 40% SDC electrolyte powder via high-speed ball milling. Then the mixed powders were calcined at 1100 °C for 5 h to obtain the NiO–SDC composite anode powder. The slurry for the YSB bilayer electrolyte coating was prepared as follows. First, the YSB electrolyte powder was added to the ethanol (solvent) in a weight ratio 1:2 and ball-milled for 24 h. Second, α-terpineol (dispersant), butyl vinyl butyral (binder), and di-n-butyl phthalate (plasticizer) were added to the solvent mixture. Finally, the slurry was ball-milled for 24 h to prepare YSB bilayer electrolyte slurry. The weight ratio between dispersant: binder: plasticizer was 1:3:2. The Ag–YSB, as the cathode ink, was prepared by mixing silver (I) oxide (99.8 wt%, Sigma Aldrich Sdn. Bhd.) and YSB at the weight ratio of 1:1 [44].

The NiO–SDC anode and the SDC electrolyte powders were co-pressed to fabricate NiO–SDC/SDC substrate via a uniaxial pressing

machine. The as-prepared green pellet was co-sintered at 1400 °C for 5 h and used as substrate for depositing the YSB bilayer electrolyte. The NiO-SDC/SDC substrate was dip-coated with YSB slurry and then dried in air for 20 min. The dip-coating and drying were repeated until the desired thickness was achieved. The required dry YSB bilayer electrolyte thickness of ~7.5 μm was achieved after repeating the dip-coating cycle for 5 times. The thickness value ranged from 1 to 1.5 μm after each dipping cycle. The YSB bilayer electrolyte thickness was controlled by maintaining the surface uniformity of substrate. Finally, the dip-coated YSB bilayer electrolyte film was sintered at 800 °C for 2 h. The effects of thickness on the microstructure and overall performance of the single SOFC was investigated by varying the YSB bilayer thickness from 1.5 to 7.5 μm. The NiO-SDC anode and the SDC/YSB bilayer electrolyte were coated with the Ag-YSB cathode slurry by using the slurry painting method (SPM). The prepared Ag-YSB cathode slurry was deposited on the half-cell and sintered at 800 °C for 2 h. The completed anode-supported single SOFC with different thicknesses of the YSB bilayer electrolyte is presented in Fig. 1.

2.2. Microstructure characterization and electrochemical test of the single SOFC

The thermal decomposition behaviors of the synthesized powders of Ag-YSB, YSB, SDC and NiO-SDC were investigated by thermogravimetry (TG)/differential scanning calorimetry (DSC) (Model 851, Mettler) at the temperature range from 30 °C to 1200 °C with a heating rate of 5 °C/min in air. X-ray diffraction (XRD) patterns were recorded at room temperature using an X-ray diffractometer (Shimadzu XRD-6000) with CuKα ($\lambda = 1.5418 \text{ \AA}$) radiation and 2θ ranging from 20° to 80° to identify the crystalline phase of all the synthesized powders. The microstructure of the fabricated anode-supported single SOFC was observed using field emission scanning electron microscopy (FESEM, Zeiss Supra-55 V P, Germany). The elemental distribution of the fabricated anode-supported single SOFC was determined through energy-dispersive X-ray spectroscopy (EDS). The effect of YSB electrolyte thickness on the electrochemical performance of the fabricated single SOFCs was tested using a solid oxide fuel cell test machine (CHINO, Japan) from 500 °C to 600 °C using hydrogen (60 mL/min) and air (100 mL/min) as the fuel and oxidant, respectively. The effective working area of the pellet was 0.8 cm². The current (*I*)-voltage (*V*) and power density (*P*) curves were measured with a multi-channel Potentiostat/Galvanostat (Autolab AUT302 FRA). The electrochemical impedance spectra (EIS) were collected by a frequency response analyzer (FRA) (Autolab 302, Eco Chemie, Netherlands) under open circuit voltage condition over a frequency range of 10⁶ Hz–0.1 Hz with a 10 mV amplitude to determine the effect of YSB bilayer thickness on the single SOFC performance. The ohmic resistance (*R*₀) and total interfacial polarization resistance (*R*_p) were determined from the impedance spectra.

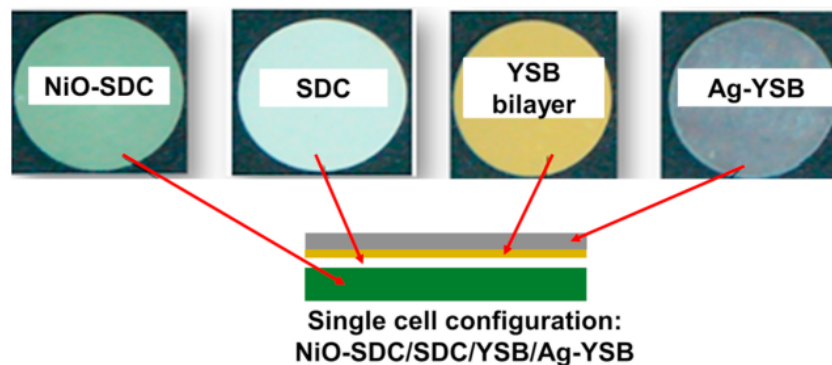


Fig. 1. Schematic configuration of NiO-SDC/SDC/YSB/Ag-YSB as a single SOFC.

3. Results and discussion

3.1. TGA/DSC analysis

The TGA/DSC analysis was conducted to examine the thermal behaviour of all the synthesized powders of Ag-YSB, YSB, SDC and NiO-SDC between 30 °C and 1200 °C, as shown in Fig. 2. No significant weight loss from the synthesized powders of NiO-SDC composite anode, SDC electrolyte and YSB bilayer electrolyte powders were observed from the TGA curve. This can be attributed to the no use of any organic and polymeric agents during the synthesis process. However, the highest weight loss was observed for the Ag-YSB cathode powders. The TGA curve showed a ~7% weight loss between 330 °C and 1000 °C for the Ag-YSB cathode powder. In the same temperature range, the DTA curve showed an endothermic peak positioned at ~950 °C, which is associated to the melting and decomposition behaviour of Ag₂O₃ in the Ag-YSB composite cathode powder. However, this decomposition behaviour of Ag₂O₃ was not observed between the actual SOFC operating temperature range between 500 and 600 °C and exhibited only ~3% weight loss between this temperature. Thus, indicating an absence of decomposition or volatilization of Ag₂O₃ during the SOFC operation and sintering temperature. Two exothermic peaks were observed from the DTA curve at ~180 °C and ~340 °C for all the synthesized powders, indicating the occurrence of glass transition phase and crystallization, respectively. This crystallization peaks at ~340 °C confirms that the crystallization

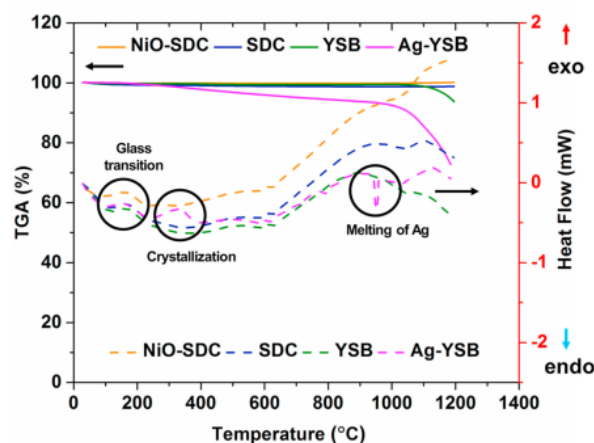


Fig. 2. TGA and DSC curve of NiO-SDC anode, SDC electrolyte, YSB bilayer electrolyte and Ag-YSB cathode powders.

occurs in the samples. These TGA and DTA data were used to determine the crystallization temperature for the synthesized powders.

3.2. XRD analysis

X-ray diffraction patterns were used to determine the phase formation and degree of crystallinity of all the synthesized powders, as shown in Fig. 3 (a)–(d). Table 1 shows the composition, phase structure, calcination temperature and crystallite size of all the synthesized powders. The phase analysis data of NiO-SDC composite anode and SDC powders confirmed that no phase changes or any chemical reaction occurred between NiO and SDC during synthesis and calcination, as shown in Fig. 3(a–b). No additional or secondary peaks as impurities were observed for the prepared composite anode powders, thereby demonstrating excellent chemical compatibility after mixing and calcination. The two main phase structures of single-crystalline cubic NiO and face-centered cubic fluorite SDC were identified. However, the crystallite size of the SDC electrolyte increased after mixing and calcination with NiO powder (Table 1). This is due to the higher calcination temperature used to prepare NiO-SDC composite anode powder (1100 °C/5 h). Fig. 3(c–d) show the XRD pattern of the YSB bilayer electrolyte and Ag-YSB composite cathode powders. The pure cubic YSB phase and main peaks of metallic Ag is evident from the XRD pattern, as shown in Fig. 3(d). A large amount of metallic Ag is detected due to low calcination temperature (600 °C/2 h) [46]. However, few Ag₂O₃ peaks were also detected. It is evident from the XRD pattern that the YSB peak shifted to lower theta angle after addition of Ag₂O₃. This peak shift can be attributed to the higher ionic radii of the six coordinated Ag²⁺ ion (0.94 Å) and could have induced the expansion of Bi₂O₃ phase [47]. The crystallite sizes of the synthesized powders were determined by the Debye-Scherrer formula ($D = 0.9\lambda / (\beta - b) \cos \theta$), where D is the crystallite size, λ is the wavelength of the X-ray radiation, β is the full width at half maximum of intensity of the fraction peak, b is standard instrumental broadening (0.0578°) and θ is the Bragg diffraction angle of peak.

3.3. Microstructure of the single SOFC

The cross-sectional FESEM micrographs of NiO-SDC/SDC anode supported single SOFC with 13 μm thick YSB bilayer electrolyte at two different magnifications are shown in Fig. 4(a–b). The anode-supported single SOFC with 1000 μm NiO-SDC composite anode, 500 μm SDC/YSB bilayer and 50 μm Ag-YSB composite is clearly distinguishable and no cracks were visible between the layers (Fig. 4 (a)). At higher magnification (Fig. 4 (b)), finer microstructure of YSB bilayer electrolyte can be distinguished between the SDC electrolyte and Ag-YSB composite

Table 1

Composition, phase structure, calcination temperature and crystallite size of the synthesized powders.

Components	Composition	Phase structure	Calcination temperature (°C)/time (hours)	Crystallite size (nm)
Electrolyte	Sm _{0.2} Ce _{0.8} O _{1.9} (SDC)	Cubic	850/5	42
Bilayer	Y _{0.25} Bi _{0.75} O _{1.5} (YSB)	Cubic	750/2	29
Anode	60 wt% NiO-40% SDC	Cubic	1100/5	116 (NiO) & 80 (SDC)
Cathode	50 wt% Ag-50% YSB	Cubic	600/2	29

cathode layers. The YSB bilayer electrolyte thickness was varied between 1.5 μm–7.5 μm and the layer appears to be porous with asymmetric grains, as shown in Fig. 5(a–b). On the other hand, the microstructure of SDC electrolyte appears to be quite dense with some closed pores. To determine for any obvious interdiffusion of constituent elements between the fabricated layers, the compositional analysis at the anode and cathode layers were conducted with the EDS technique, as shown in Fig. 4(c–d). Ni, Ce, Sm is only present in the NiO-SDC composite anode layer (Fig. 4(d)). Similarly, elements such as Ag, Bi and Y are only observed in the Ag-YSB composite cathode layer. This clearly indicates that no obvious interdiffusion of elements between the Ag-YSB and NiO-SDC layers through SDC/YSB layers was observed. This assures the stability of the layers during the fabrication and sintering processes.

As shown by the cross-sectional images in Fig. 5(a–b), the bilayer electrolyte YSB particles are homogeneously distributed along the SDC electrolyte substrate. The YSB bilayer appeared to be porous and adhered well to the SDC electrolyte and Ag-YSB composite cathode with no delamination or cracks. The YSB bilayer thickness increased gradually from 1.5 to 7.5 μm as the number of layers increased.

3.4. Single SOFC electrochemical performance

The electrochemical performance of the fabricated NiO-SDC/SDC anode-supported single SOFC with different YSB bilayer electrolyte thicknesses (1.5, 3.5, 16 and 7.5 μm) was investigated at 500 °C–600 °C in air and hydrogen. I - V and I - P characteristics of the fabricated anode supported cell with different YSB bilayer electrolyte measured at 600 °C are shown in Fig. 6. It is evident that the electrochemical performance of the fabricated anode-supported single SOFC increased as the thickness of the YSB bilayer electrolyte increased. The maximum OCV of the anode-

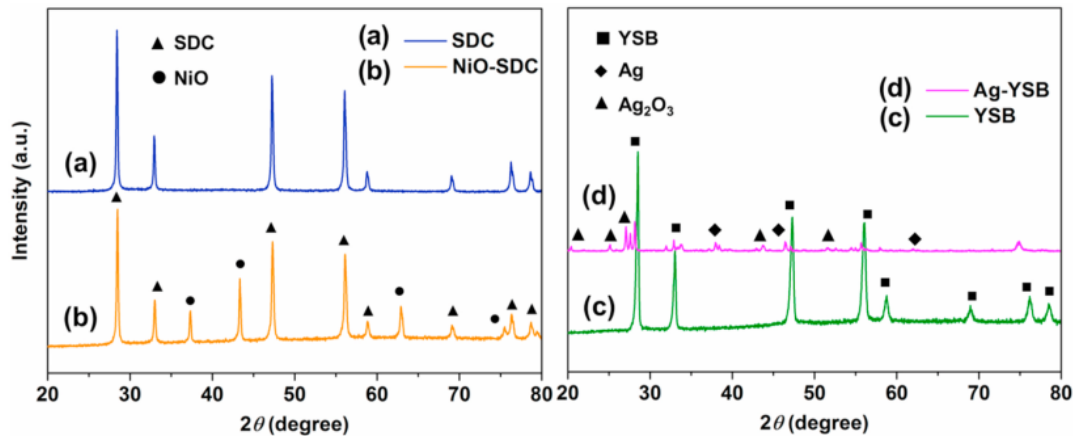


Fig. 3. XRD patterns of (a) NiO-SDC composite anode, (b) SDC electrolyte, (c) YSB bilayer electrolyte, (d) Ag-YSB cathode powders.

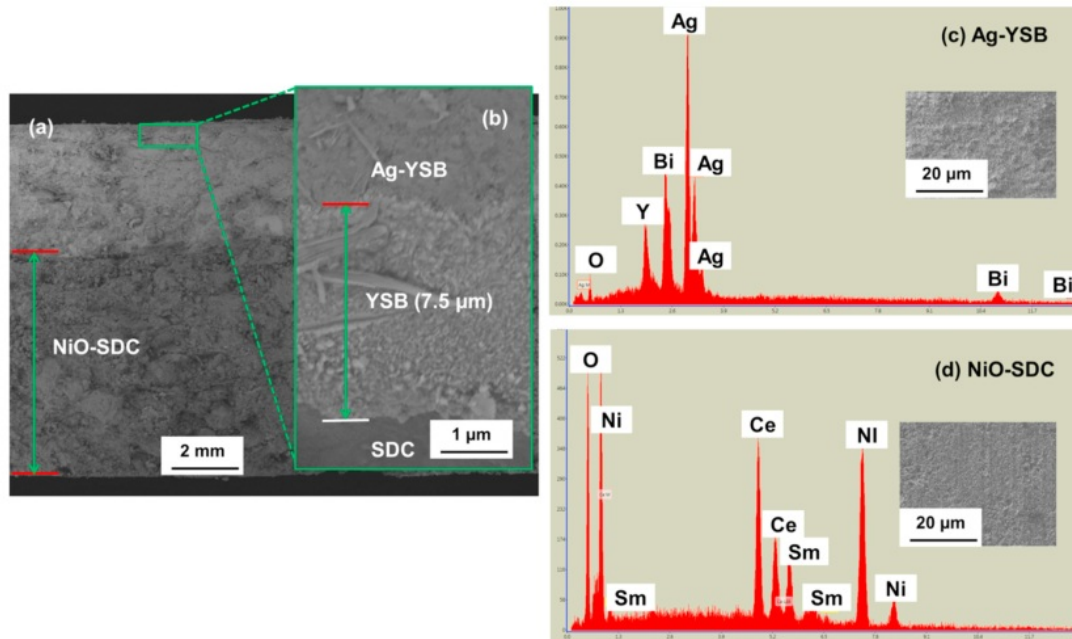


Fig. 4. Cross-sectional FESEM images of NiO-SDC/SDC/YSB/Ag-YSB single SOFC at two different magnification: (a) 80 \times and (b) 10,000 \times ; EDS elemental analysis of: (c) Ag-YSB composite cathode, and (d) NiO-SDC composite anode.

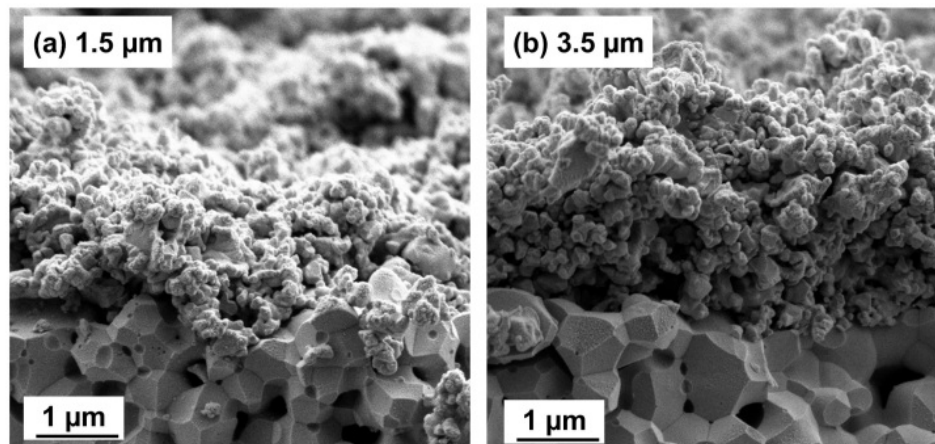


Fig. 5. FESEM image of the YSB bilayer electrolytes with different thicknesses (a) 1.5, and (b) 3.5 μm .

supported single SOFC with different thicknesses of 1.5, 3.5, 5.5 and 7.5 μm reached 0.99 V, 1.074 V, 1.068 V, and 1.072 V, respectively at an operating temperature of 600 $^{\circ}\text{C}$. Moreover, it is noteworthy that the OCVs of all the fabricated single SOFCs were extremely close to the theoretical values, due to the high dense SDC electrolyte as observed in Fig. 4(b) [36]. The maximum power densities of the NiO-SDC/SDC anode supported cells at 600 $^{\circ}\text{C}$ with YSB bilayer thicknesses of 1.5, 3.5, 5.5 and 7.5 μm were 26.3, 61.5, 86, and 79.2 mW/cm^2 , respectively. As shown in Fig. 6, the single SOFC with 5.5 μm -thick YSB bilayer electrolytes exhibited a maximum power density of 86 mW/cm^2 and a current density of 259.5 mA/cm^2 at 600 $^{\circ}\text{C}$. All of the anode-supported single SOFCs in this study were manufactured in a similar way but exhibited different OCVs and power densities due to the variations in thickness of the YSB bilayer electrolyte. Jaiswal et al. [37] also reported

a similar finding for bismuth-based bilayer electrolyte materials with relatively high thicknesses. This indicates that electrochemical performance of the NiO-SDC/SDC anode supported single SOFC can be increased by forming a pure oxide-ion conducting and electron-blocking functional layer [40]. Moreover, the presence of thick SDC layer is beneficial to YSB electrolyte stability. The YSB bilayer electrolyte materials in this study yielded higher OCV results than those in previous research. For instance, Zhang et al. [19] investigated a single cell with SDC/SDC/YSB/LSM-YSM configuration and reported the maximum OCV value of 0.897 V at 600 $^{\circ}\text{C}$. From Fig. 7 (a)-(c), it is evident that the maximum power density increased from 14.8 mW/cm^2 to 86 mW/cm^2 as the operating temperature increased from 500 to 600 $^{\circ}\text{C}$. This is due to increased ionic conductivity of the electrolyte and faster electrode catalytic activity with the increasing temperature [48].

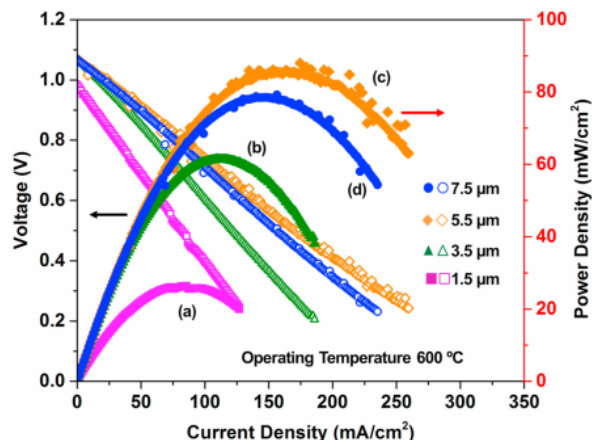


Fig. 6. Electrochemical performance of single SOFC with different YSB bilayer thicknesses at 600 °C: (a) 1.5 μm, (b) 3.5 μm, (c) 5.5 μm, and (d) 7.5 μm.

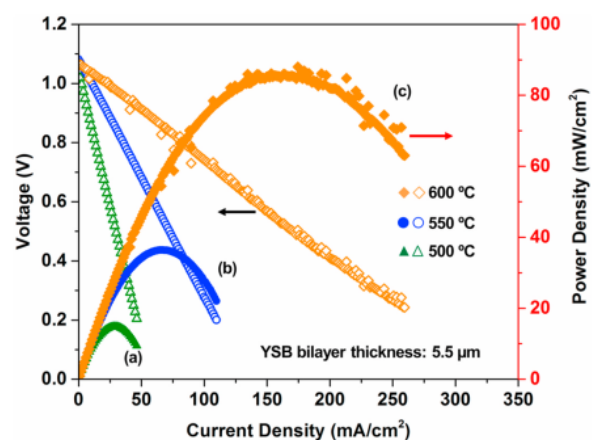


Fig. 7. Electrochemical performance of a single SOFC with 5.5 μm thick YSB bilayer thicknesses at: (a) 500 °C, (b) 550 °C, and (c) 600 °C.

The effect of the thickness variation of the YSB bilayer electrolyte on the performance difference needs to be further explored. Thus, the EIS technique was employed on the single SOFCs at 600 °C. Fig. 8 shows the corresponding impedance spectra measured at 600 °C for the NiO-SDC/SDC anode supported cell with different YSB bilayer electrolytes. The following equivalent circuit (insert) was used to investigate the electrical behaviour at 600 °C, where R_{ele} is the ohmic resistance from the electrolyte (first semicircle at high frequency), R_{cath} is attributed to the charge transfer resistance from the cathode (second semicircle at middle frequency), R_{ano} is attributed to the gas diffusion resistance at the anode (third semicircle at low frequency), and CPE is the constant phase element. All the samples exhibited three arcs in the complex impedance plane featuring the frequency-dependent semicircles related to the electrolyte (R_{ele}) cathode (R_{cath}) and anode (R_{ano}) responses, respectively. The ohmic resistance of the electrolyte/bilayer electrolyte decreased as the YSB bilayer electrolyte thickness increased to 5.5 μm and began to increase again when YSB bilayer electrolyte is > 5.5 μm. The ohmic resistance was found to be 4.95 Ωcm², 3.27 Ωcm², 3.1 Ωcm² and 3.21 Ωcm² for the single SOFC with 1.5, 3.5, 5.5, and 7.5 μm-thick YSB bilayer electrolytes, respectively. Moreover, the total polarization resistance (R_{tot}) of the anode-supported cell also decreased as the YSB bilayer thickness increased. The R_{tot} of the anode-supported single

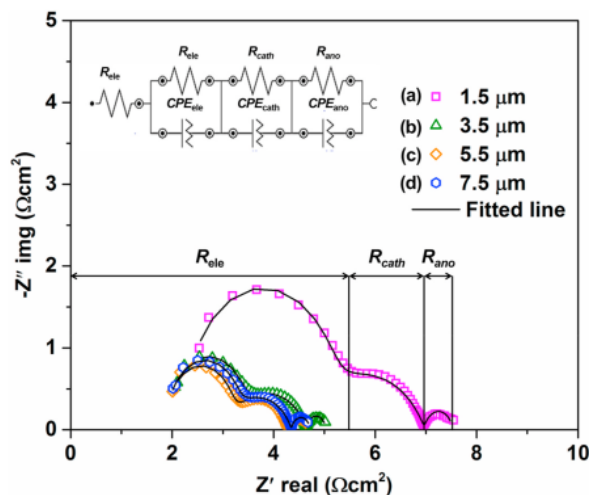


Fig. 8. Impedance spectra of the anode-supported single SOFC with different YSB bilayer thicknesses at 600 °C: (a) 1.5 μm, (b) 3.5 μm, (c) 5.5 μm, and (d) 7.5 μm.

SOFC was calculated using the sum of both ohmic resistance and interfacial polarization resistance from the electrolyte and electrodes, respectively. The total resistance was found to be 7.53 Ωcm², 5.03 Ωcm², 4.64 Ωcm² and 4.73 Ωcm² for the fabricated single SOFCs with 1.5, 3.5, 5.5, and 7.5 μm-thick YSB bilayer electrolytes, respectively. This decrease in total polarization resistance was greatly influenced by the interfacial polarization resistance ($R_p = R_{cath} + R_{ano}$) from the electrodes, especially from the cathode side.

The cathodic polarization resistance (R_{cath}) from the Ag-YSB cathode decreased as the YSB bilayer thickness increased from 1.5 μm to 7.5 μm as shown in Fig. 8. The R_{cath} value was found to be 2.53 Ωcm², 1.73 Ωcm², 1.48 Ωcm² and 1.43 Ωcm² for the single SOFC with 1.5, 3.5, 5.5, and 7.5 μm-thick YSB bilayer electrolytes, respectively. Because of the high conductivity of the YSB electrolyte, it is apparent that the ohmic resistance of the anode-supported single SOFC did not demonstrate a noticeable change due to the increase in the thickness of the YSB bilayer electrolyte. However, the R_p of the anode-supported single SOFC with 5.5 μm-thick YSB bilayer electrolyte was much lower than that of the single SOFC with 1.5 μm-thick YSB bilayer electrolyte due to the positive effect of the YSB bilayer on cathodic polarization. This decrease in R_{cath} can be attributed to the increased thickness of the YSB bilayer electrolyte. The explanation for this is that the YSB bilayer electrolyte demonstrates a pure ion-conducting oxide behaviour that enhanced the oxygen dissociation and surface oxygen exchange rate [33,49]. This is because the bilayer electrolyte can be used as both an electronic conduction barrier and an oxygen-ion-conducting phase in the cathode structure, thus, the YSB bilayer electrolyte, as a pure oxide ion conductor, manifested positive effect [21]. It should be noted that the increase in maximum power density for single SOFC with 5.5 μm-thick YSB electrolyte is a function of the operating temperature and YSB bilayer thickness. Therefore, an improvement in the thickness of the YSB bilayer electrolyte contributes to an increase in the length of the ion transfer pathway in the electrolyte, which leads to an increase in the power density. The sample with the 5.5 μm-thick YSB bilayer electrolyte exhibited low total resistance (4.64 Ωcm²) at 600 °C. However, the performance obtained from this study was lower or simply comparable with the reported values for several bismuth bilayer electrolyte-based fuel cells (Table 2). The differences in performance between the present and previous studies can be explained by the variation in materials and bilayer electrolyte thickness. Therefore, the optimization of material compositions, fabrication parameters, and electrolyte and bilayer electrolyte thickness could contribute to the

Table 2
Comparison of single-cell performance of bismuth bilayer electrolyte materials.

Single SOFC configuration: Anode/Electrolyte/Bilayer/Cathode	Bilayer thickness (μm)	Operating temperature ($^{\circ}\text{C}$)	Power density (mW/cm^2)	Reference
NiO-SDC/SDC/YSB/Ag-YSB	5.5	600	86	This study
NiO-GDC/GDC/xSB/LSM-ESB	20.6	650	1060	[37]
NiCuO-SNDC/SNDC/ESB/LSM-ESB	20	450	129	[40]
NiO-BCZY/BCZY/BY/SSC-SDC	3.6	700	163	[42]
Pt/SDC/Au	–	800	40	[50]
NiO-YSZ/YSZ/ESB/LSM-ESB	5.1	700	2100	[51]

increase in the OCV value and overall performance of the fuel cell.

4. Conclusion

The dip-coating technique was used in this study to coat the YSB electronic blocking functional layer on the NiO-SDC/SDC substrate. The YSB thickness was varied from 1.5 to 7.5 μm . The OCV values were 0.99 V, 1.074 V, 1.068 V, and 1.072 V, while the respective YSB layer thicknesses were 1.5, 3.5, 5.5 and 7.5 at 600 $^{\circ}\text{C}$. The result indicates that thick YSB layers can block the electronic conduction in SDC electrolytes and increased the OCV values compared with cells with <5.5 μm thickness. The single SOFC with 5.5 μm -thick YSB bilayer electrolytes exhibited a maximum power density of 86 mW/cm^2 and a current density of 259.5 mA/cm^2 at 600 $^{\circ}\text{C}$. However, the power densities of the cells obtained from this study are not high enough for low-to intermediate-temperature SOFC operation. Thus, further improvement is needed to expand the ionic conductivity of bilayer electrolytes.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgments

This work was supported by Universiti Kebangsaan Malaysia (UKM), Universiti Teknologi Petronas, and Universitas Islam Riau under the research sponsorships of MI/2019/019, 468/Kontrak/LPM-UIR-9-2018, and 361/Kontrak/LPPM-UIR/4-2018, respectively. The authors would also like to acknowledge the support of the Centre for Research and Instrumentation Management, UKM, for the testing equipment.

References

- R. Raza, B. Zhu, A. Rafique, M.R. Naqvi, P. Lund, Functional ceria-based nanocomposites for advanced low-temperature (300–600 $^{\circ}\text{C}$) solid oxide fuel cell: a comprehensive review, *Mater. Today Energy* 15 (2020), 100373.
- A.M. Hussain, K.-J. Pan, I.A. Robinson, T. Hays, E.D. Wachsman, Stannate-based ceramic oxide as anode materials for oxide-ion conducting low-temperature solid oxide fuel cells, *J. Electrochem. Soc.* 163 (2016) F1198–F1205.
- C. Zhou, J. Sunarso, Y. Song, J. Dai, J. Zhang, B. Gu, W. Zhou, Z. Shao, New reduced-temperature ceramic fuel cells with dual-ion conducting electrolyte and triple-conducting double perovskite cathode, *J. Mater. Chem. A* 7 (2019) 13265–13274.
- T.B. Mitchell-Williams, R.L. Tomov, S.A. Saadabadi, M. Krauz, P.V. Aravind, B. A. Glowacki, R.V. Kumar, Infiltration of commercially available, anode supported SOFCs via inkjet printing, *Mater. Renew. Sustain. Energy* 6 (2017) 12.
- Y.L. Huang, A.M. Hussain, E.D. Wachsman, Nanoscale cathode modification for high performance and stable low-temperature solid oxide fuel cells (SOFCs), *Nanomater. Energy* 49 (2018) 186–192.
- S.P.S. Shaikh, A. Mughtar, M.R. Somalu, A review on the selection of anode materials for solid-oxide fuel cells, *Renew. Sustain. Energy Rev.* 51 (2015) 1–8.
- M. Anwar, M.A. Muhammed, A. Mughtar, M.R. Somalu, Influence of strontium co-doping on the structural, optical, and electrical properties of erbium-doped ceria electrolyte for intermediate temperature solid oxide fuel cells, *Ceram. Int.* 45 (2019) 5627–5636.
- S.A. Muhammed Ali, M. Anwar, L.S. Mahmud, N.S. Kalib, A. Mughtar, M. R. Somalu, Influence of current collecting and functional layer thickness on the performance stability of La_{0.6}Sr_{0.4}Co_{0.2}Fe_{0.8}O_{3- δ} -Ce_{0.8}Sm_{0.2}O_{1.9} composite cathode, *J. Solid State Electrochem.* 23 (2019) 1155–1164.
- N. Hedayat, D. Panthi, Y. Du, Fabrication of anode-supported microtubular solid oxide fuel cells by sequential dip-coating and reduced sintering steps, *Electrochim. Acta* 258 (2017) 694–702.
- Y.C. Yang, P.H. Wang, Y.T. Tsai, H.C. Ong, Influences of feedstock and plasma spraying parameters on the fabrication of tubular solid oxide fuel cell anodes, *Ceram. Int.* 44 (2018) 7824–7830.
- T. Pirasaci, Non-uniform, multi-stack solid oxide fuel cell (SOFC) system design for small system size and high efficiency, *J. Power Sources* 426 (2019) 135–142.
- A.M. Soydan, Ö. Yıldız, A. Durğun, O.Y. Akduman, A. Ata, Production, performance and cost analysis of anode-supported NiO-YSZ micro-tubular SOFCs, *Int. J. Hydrogen Energy* 44 (2019) 30339–30347.
- A.D. Handoko, S.N. Steinmann, Z.W. Seh, Theory-guided materials design: two-dimensional MXenes in electro- and photocatalysis, *Nanoscale Horizons* 4 (2019) 809–827.
- Z.W. Seh, J. Kibsgaard, C.F. Dickens, I. Chorkendorff, J.K. Nørskov, T.F. Jaramillo, Combining theory and experiment in electrocatalysis: insights into materials design, *Science* 345 (2017) 4998.
- Y. Lyu, J. Xie, D. Wang, J. Wang, Review of cell performance in solid oxide fuel cells, *J. Mater. Sci.* 55 (2020) 7184–7207.
- S.P. Jiang, Development of lanthanum strontium cobalt ferrite perovskite electrodes of solid oxide fuel cells – a review, *Int. J. Hydrogen Energy* 44 (2019) 7448–7493.
- S. Cho, Y. Kim, J.H. Kim, A. Manthiram, H. Wang, High power density thin film SOFCs with YSZ/GDC bilayer electrolyte, *Electrochim. Acta* 56 (2011) 5472–5477.
- J.S. Ahn, M.A. Camaratta, D. Pergolesi, K.T. Lee, H. Yoon, B.W. Lee, D.W. Jung, E. Traversa, E.D. Wachsman, Development of high performance ceria/bismuth oxide bilayered electrolyte SOFCs for lower temperature operation, *J. Electrochem. Soc.* 157 (2010) B376.
- L. Zhang, C. Xia, F. Zhao, F. Chen, Thin film ceria-bismuth bilayer electrolytes for intermediate temperature solid oxide fuel cells with La_{0.85}Sr_{0.15}MnO_{3- δ} - δ -Y_{0.25}Bi_{0.75}O_{1.5} cathodes, *Mater. Res. Bull.* 45 (2010) 603–608.
- A.L. Ruth, K.T. Lee, M. Clites, E.D. Wachsman, Synthesis and characterization of double-doped bismuth oxide electrolytes for lower temperature SOFC application, *ECS Trans* 64 (2014) 135–141.
- G. Li, B. He, Y. Ling, J. Xu, L. Zhao, Highly active YSB infiltrated LSCF cathode for proton conducting solid oxide fuel cells, *Int. J. Hydrogen Energy* 40 (2015) 13576–13582.
- H. Ozlu Torun, S. Cakar, E. Ersoy, O. Turkoglu, The bulk electrical conductivity properties of δ -Bi₂O₃ solid electrolyte system doped with Yb₂O₃, *J. Therm. Anal. Calorim.* 122 (2015) 525–536.
- E.D. Wachsman, K.T. Lee, Lowering the temperature of solid oxide fuel cells, *Science* 334 (80) (2011) 935–939.
- J.Y. Park, E.D. Wachsman, Stable and high conductivity ceria/bismuth oxide bilayer electrolytes for lower temperature solid oxide fuel cells, *Ionics* 12 (2006) 15–20.
- M. Biswas, K. Sadanala, Electrolyte materials for solid oxide fuel cells (SOFCs), *Powder Metall. Min.* 2 (2013) 26–55.
- M. Liu, F. Uba, Y. Liu, A high-performance solid oxide fuel cell with a layered electrolyte for reduced temperatures, *J. Am. Ceram. Soc.* 103 (2020) 5325–5336.
- M. Anwar, S.A. Muhammed Ali, A. Mughtar, M.R. Somalu, Synthesis and characterization of M-doped ceria-termary carbonate composite electrolytes (M = erbium, lanthanum and strontium) for low-temperature solid oxide fuel cells, *J. Alloys Compd.* 775 (2019) 571–580.
- Y.D. Kim, J. Yang, J.I. Lee, M. Saqib, J.S. Shin, K. Park, M. Jo, S.J. Song, J.Y. Park, Degradation studies of ceria-based solid oxide fuel cells at intermediate temperature under various load conditions, *J. Power Sources* 452 (2020) 227758.
- J. Kim, J. Kim, K.J. Yoon, J.-W. Son, J.-H. Lee, J.-H. Lee, H.-W. Lee, H.-I. Ji, Solid oxide fuel cells with zirconia/ceria bilayer electrolytes via roll calendaring process, *J. Alloys Compd.* 846 (2020) 156318.
- C. Kim, S. Kim, I. Jang, H. Yoon, T. Song, U. Paik, Facile fabrication strategy of highly dense gadolinium-doped ceria/yttria-stabilized zirconia bilayer electrolyte via cold isostatic pressing for low temperature solid oxide fuel cells, *J. Power Sources* 415 (2019) 112–118.
- P. Coddet, M.L. Amany, J. Vulliet, A. Caillard, A.L. Thomann, YSZ/GDC bilayer and gradient barrier layers deposited by reactive magnetron sputtering for solid oxide cells, *Surf. Coating. Technol.* 357 (2019) 103–113.
- D. Heidari, S. Javadpour, S.H. Chan, An evaluation of electrochemical performance of a solid oxide electrolyzer cell as a function of co-sintered YSZ-SDC bilayer electrolyte thickness, *Energy Convers. Manag.* 150 (2017) 567–573.
- J.S. Ahn, D. Pergolesi, M.A. Camaratta, H. Yoon, B.W. Lee, K.T. Lee, D.W. Jung, E. Traversa, E.D. Wachsman, High-performance bilayered electrolyte intermediate temperature solid oxide fuel cells, *Electrochem. Commun. Now.* 11 (2009) 1504–1507.
- N. Jiang, E.D. Wachsman, S.H. Jung, A higher conductivity Bi₂O₃-based electrolyte, *Solid State Ionics* 150 (2002) 347–353.

- [35] K.T. Lee, D.W. Jung, M.A. Camaratta, H.S. Yoon, J.S. Ahn, E.D. Wachsman, Gd_{0.1}Ce_{0.9}O_{1.95}/Er_{0.4}Bi_{1.6}O₃ bilayered electrolytes fabricated by a simple colloidal route using nano-sized Er_{0.4}Bi_{1.6}O₃ powders for high performance low temperature solid oxide fuel cells, *J. Power Sources* 205 (2012) 122–128.
- [36] D.W. Joh, J.H. Park, D. Kim, E.D. Wachsman, K.T. Lee, Functionally graded bismuth oxide/zirconia bilayer electrolytes for high-performance intermediate-temperature solid oxide fuel cells (IT-SOFCs), *ACS Appl. Mater. Interfaces* 9 (2017) 8443–8449.
- [37] A. Jaiswal, A. Pesaran, S. Omar, E.D. Wachsman, Ceria/bismuth oxide bilayer electrolyte based low-temperature SOFCs with stable electrochemical performance, *ECS Trans* 78 (2017) 361–370.
- [38] J. Hou, L. Bi, J. Qian, Z. Zhu, J. Zhang, W. Liu, High performance ceria-bismuth bilayer electrolyte low temperature solid oxide fuel cells (LT-SOFCs) fabricated by combining co-pressing with drop-coating, *J. Mater. Chem. A* 3 (2015) 10219–10224.
- [39] A. Pesaran, A. Jaiswal, Y. Ren, E.D. Wachsman, Development of a new ceria/yttria-ceria double-doped bismuth oxide bilayer electrolyte low-temperature SOFC with higher stability, *Ionics* 25 (2019) 3153–3164.
- [40] L. Miao, J. Hou, K. Dong, W. Liu, A strategy for improving the sinterability and electrochemical properties of ceria-based LT-SOFCs using bismuth oxide additive, *Int. J. Hydrogen Energy* 44 (2019) 5447–5453.
- [41] Y.D. Kim, J.Y. Yang, J.I. Lee, M. Saqib, J.S. Shin, M. Shin, J.H. Kim, H.T. Lim, J. Y. Park, Stable ceria-based electrolytes for intermediate temperature-solid oxide fuel cells via hafnium oxide blocking layer, *J. Alloys Compd.* 779 (2019) 121–128.
- [42] J. Qian, W. Sun, Q. Zhang, G. Jiang, W. Liu, Fabrication and performance of BaCe_{0.8}Y_{0.2}O_{3-δ}-BaZr_{0.8}Y_{0.2}O_{3-δ} bilayer electrolyte for anode-supported solid oxide fuel cells, *J. Power Sources* 249 (2014) 131–136.
- [43] L.S. Wang, C.X. Li, C.J. Li, G.J. Yang, Performance of La_{0.8}Sr_{0.2}Ga_{0.8}Mg_{0.2}O₃-based SOFCs with atmospheric plasma sprayed La-doped CeO₂ buffer layer, *Electrochim. Acta* 275 (2018) 208–217.
- [44] D. Panuh, A. Muchtar, N. Muhamad, E.H. Majlan, W.R.W. Daud, Fabrication of thin Ag-YSB composite cathode film for intermediate-temperature solid oxide fuel cells, *Compos. B Eng.* 58 (2014) 193–198.
- [45] A. Bodén, J. Di, C. Lagergren, G. Lindbergh, C.Y. Wang, Conductivity of SDC and (Li/Na)₂CO₃ composite electrolytes in reducing and oxidising atmospheres, *J. Power Sources* 172 (2007) 520–529.
- [46] R. Sazinas, K.B. Andersen, S.B. Simonsen, P. Holtappels, K.K. Hansen, Silver modified cathodes for solid oxide fuel cells, *J. Electrochem. Soc.* 166 (2019) F79–F88.
- [47] R.D. Shannon, Revised effective ionic radii and systematic studies of interatomic distances in halides and chalcogenides, *Acta Crystallogr. A* 32 (1976) 751–767.
- [48] W. Sun, N. Zhang, Y. Mao, K. Sun, Facile one-step fabrication of dual-pore anode for planar solid oxide fuel cell by the phase inversion, *Electrochem. Commun.* 22 (2012) 41–44.
- [49] A. Pesaran, A. Jaiswal, E.D. Wachsman, Bilayer electrolytes for low temperature and intermediate temperature solid oxide fuel cells – a review, in: S. Skinner (Ed.), *Energy Storage Convers. Mater.*, The Royal Society of Chemistry, 2019, pp. 1–41.
- [50] E.D. Wachsman, P. Jayaweera, N. Jiang, D.M. Lowe, B.G. Pound, Stable high conductivity ceria/bismuth oxide bilayered electrolytes, *J. Electrochem. Soc.* 144 (1997) 233–236.
- [51] D.W. Joh, J.H. Park, D. Kim, E.D. Wachsman, K.T. Lee, Functionally graded bismuth oxide/zirconia bilayer electrolytes for high-performance intermediate-temperature solid oxide fuel cells (IT-SOFCs), *ACS Appl. Mater. Interfaces* 9 (2017) 8443–8449.

Effect of yttrium-stabilized bismuth

ORIGINALITY REPORT

20%

SIMILARITY INDEX

4%

INTERNET SOURCES

19%

PUBLICATIONS

0%

STUDENT PAPERS

PRIMARY SOURCES

- 1** Jun-Young Park, Eric D. Wachsman. "Stable and high conductivity ceria/bismuth oxide bilayer electrolytes for lower temperature solid oxide fuel cells", Ionics, 2006 **1%**

Publication
 - 2** Haibin Sun, Yu Chen, Ruiqiang Yan, Tao Wei, Yujun Zhang, Qiaobao Zhang, Yunfei Bu, Meilin Liu. "Anode-supported solid oxide fuel cells based on Sm_{0.2}Ce_{0.8}O_{1.9} electrolyte fabricated by a phase-inversion and drop-coating process", International Journal of Hydrogen Energy, 2016 **1%**

Publication
 - 3** Dong Woo Joh, Jeong Hwa Park, Doyeub Kim, Eric D. Wachsman, Kang Taek Lee. "Functionally Graded Bismuth Oxide/Zirconia Bilayer Electrolytes for High-Performance Intermediate-Temperature Solid Oxide Fuel Cells (IT-SOFCs)", ACS Applied Materials & Interfaces, 2017 **1%**

Publication
-

4

Alireza Pesaran, Abhishek Jaiswal, Yaoyu Ren, Eric D. Wachsman. "Development of a new ceria/yttria-ceria double-doped bismuth oxide bilayer electrolyte low-temperature SOFC with higher stability", Ionics, 2019

Publication

1%

5

Jong-Eun Hong, Toru Inagaki, Shintaro Ida, Tatsumi Ishihara. "Improved power generation performance of solid oxide fuel cells using doped LaGaO₃ electrolyte films prepared by screen printing method II. Optimization of Ni–Ce_{0.8}Sm_{0.2}O_{1.9} cermet anode support", International Journal of Hydrogen Energy, 2011

Publication

1%

6

Zhu, C.. "Preparation and performance of Pr_{0.7}Sr_{0.3}Co_{1-y}Cu_yO_{3-δ} as cathode material of IT-SOFCs", Solid State Ionics, 20080930

Publication

1%

7

Sea-Fue Wang, His-Chuan Lu, Yung-Fu Hsu, Yi-Xuan Hu. "Solid oxide fuel cells with (La,Sr)(Ga,Mg)O_{3-δ} electrolyte film deposited by radio-frequency magnetron sputtering", Journal of Power Sources, 2015

Publication

1%

8

Hemanshu D Bhatt, Ramakrishna Vedula, Seshu B Desu, Gustave C Fralick.

1%

"La(1-x)SrxCoO3 for thin film thermocouple applications", Thin Solid Films, 1999

Publication

9

Lei Zhang, Lan Li, Fei Zhao, Fanglin Chen, Changrong Xia.

"Sm0.2Ce0.8O1.9/Y0.25Bi0.75O1.5 bilayered electrolytes for low-temperature SOFCs with Ag-Y0.25Bi0.75O1.5 composite cathodes", Solid State Ionics, 2011

Publication

1%

10

Nader Hedayat, Dhruva Panthi, Yanhai Du.

"Fabrication of anode-supported microtubular solid oxide fuel cells by sequential dip-coating and reduced sintering steps", Electrochimica Acta, 2017

Publication

<1%

11

Chanho Kim, Sungmin Kim, Inyoung Jang, Heesung Yoon, Taeseup Song, Ungyu Paik.

"Facile fabrication strategy of highly dense gadolinium-doped ceria/yttria-stabilized zirconia bilayer electrolyte via cold isostatic pressing for low temperature solid oxide fuel cells", Journal of Power Sources, 2019

Publication

<1%

12

Caroline A. Cobine, Grant W. Hennig, Masaaki Kurahashi, Kenton M. Sanders, Sean M. Ward, Kathleen D. Keef. "Relationship between

<1%

interstitial cells of Cajal, fibroblast-like cells and inhibitory motor nerves in the internal anal sphincter", Cell and Tissue Research, 2011

Publication

13

Cuijuan Zhang, Kevin Huang. "A new composite cathode for intermediate temperature solid oxide fuel cells with zirconia-based electrolytes", Journal of Power Sources, 2017

<1%

Publication

14

Neelima Mahato, Amitava Banerjee, Alka Gupta, Shobit Omar, Kantesh Balani. "Progress in material selection for solid oxide fuel cell technology: A review", Progress in Materials Science, 2015

<1%

Publication

15

Lee, Jin Goo, Jeong Ho Park, and Yong Gun Shul. "Tailoring gadolinium-doped ceria-based solid oxide fuel cells to achieve 2 W cm⁻² at 550 °C", Nature Communications, 2014.

<1%

Publication

16

Lina Miao, Jie Hou, Kuan Dong, Wei Liu. "A strategy for improving the sinterability and electrochemical properties of ceria-based LT-SOFCs using bismuth oxide additive", International Journal of Hydrogen Energy, 2018

<1%

Publication

17

Fang, S.. "Effect of microstructure and catalyst

coating on the oxygen permeability of a novel CO₂-resistant composite membrane", Solid State Ionics, 20110519

Publication

<1%

18

Jing Qian, Wenping Sun, Qingping Zhang, Guoshun Jiang, Wei Liu. "Fabrication and performance of BaCe_{0.8}Y_{0.2}O_{3-δ}-BaZr_{0.8}Y_{0.2}O_{3-δ} bilayer electrolyte for anode-supported solid oxide fuel cells", Journal of Power Sources, 2014

Publication

<1%

19

Xiao, Yaoming, Chenlu Wang, and Gaoyi Han. "Effects of thiourea concentration on electrocatalytic performances of nickel sulfide counter electrodes for use in dye-sensitized solar cells", Materials Research Bulletin, 2015.

Publication

<1%

20

Gurbinder Kaur. "Solid Oxide Fuel Cell Components", Springer Science and Business Media LLC, 2016

Publication

<1%

21

d-nb.info

Internet Source

<1%

22

Liu, H.. "Structural, electrochemical and thermal properties of LiNi_{0.8}-yTi_yCo_{0.2}O₂ as cathode materials for lithium ion battery", Electrochimica Acta, 20040315

<1%

23

Zongping Shao, Moses O. Tadé. "Intermediate-Temperature Solid Oxide Fuel Cells", Springer Science and Business Media LLC, 2016

Publication

<1%

24

Zhicheng Wang, Wenjian Weng, Kui Cheng, Piyi Du, Ge Shen, Gaorong Han. "Catalytic modification of Ni–Sm-doped ceria anodes with copper for direct utilization of dry methane in low-temperature solid oxide fuel cells", Journal of Power Sources, 2008

Publication

<1%

25

Sungmee Cho, YoungNam Kim, Jung-Hyun Kim, Arumugam Manthiram, Haiyan Wang. "High power density thin film SOFCs with YSZ/GDC bilayer electrolyte", Electrochimica Acta, 2011

Publication

<1%

26

Ya-Ping Wang, Kai Zhao, Qing Xu, Duan-Ping Huang, Min Chen, Bok-Hee Kim. "Optimization on the electrochemical properties of La₂NiO_{4+δ} cathodes by tuning the cathode thickness", International Journal of Hydrogen Energy, 2018

Publication

<1%

27

Cao, Jiafeng, Zheng Gong, Chuangang Fan, Yuexia Ji, and Wei Liu. "The improvement of barium-containing anode for ceria-based

<1%

electrolyte with electron-blocking layer", Journal of Alloys and Compounds, 2017.

Publication

28

Zhu, B.. "Solid oxide fuel cell (SOFC) using industrial grade mixed rare-earth oxide electrolytes", International Journal of Hydrogen Energy, 200807

Publication

29

Jing Qian, Zetian Tao, Jin Xiao, Guoshun Jiang, Wei Liu. "Performance improvement of ceria-based solid oxide fuel cells with yttria-stabilized zirconia as an electronic blocking layer by pulsed laser deposition", International Journal of Hydrogen Energy, 2013

Publication

30

Sun, C.. "Investigations of mesoporous CeO₂-Ru as a reforming catalyst layer for solid oxide fuel cells", Electrochemistry Communications, 200605

Publication

31

Ji-Seop Shin, Hyunyoung Park, Kwangho Park, Muhammad Saqib et al. " Activity of layered swedenborgite structured Y Er BaCo Ga O for oxygen electrode reactions in at intermediate temperature reversible ceramic cells ", Journal of Materials Chemistry A, 2021

Publication

<1%

<1%

<1%

<1%

32

Rui Chen, Shan-Lin Zhang, Chang-Jiu Li, Cheng-Xin Li. "Plasma-Sprayed High-Performance (Bi₂O₃)_{0.75}(Y₂O₃)_{0.25} Electrolyte for Intermediate-Temperature Solid Oxide Fuel Cells (IT-SOFCs)", Journal of Thermal Spray Technology, 2021

Publication

<1%

33

ira.lib.polyu.edu.hk

Internet Source

<1%

34

journalarticle.ukm.my

Internet Source

<1%

35

Qing Su, Daeil Yoon, Aiping Chen, Fauzia Khatkhatay, Arumugam Manthiram, Haiyan Wang. "Vertically aligned nanocomposite electrolytes with superior out-of-plane ionic conductivity for solid oxide fuel cells", Journal of Power Sources, 2013

Publication

<1%

36

Lei Bi, Enrico Traversa. " Synthesis strategies for improving the performance of doped-BaZrO materials in solid oxide fuel cell applications ", Journal of Materials Research, 2013

Publication

<1%

37

Kang Taek Lee, Doh Won Jung, Hee Sung Yoon, Ashley A. Lidie, Matthew A. Camaratta, Eric D. Wachsman. "Interfacial modification of

<1%

La_{0.80}Sr_{0.20}MnO_{3-δ}-Er_{0.4}Bi_{0.6}O₃ cathodes for high performance lower temperature solid oxide fuel cells", Journal of Power Sources, 2012

Publication

38

Itahara, Hiroshi, Changtai Xia, Jun Sugiyama, and Toshihiko Tani. "Fabrication of textured thermoelectric layered cobaltites with various rock salt-type layers by using \hat{I}^2 -Co(OH)₂ platelets as reactive templates", Journal of Materials Chemistry, 2004.

Publication

39

Liang Wang, Piaopiao Wang, Chaoliang Geng, Hang Cao, Chenxi Xu, Jigui Cheng, Tao Hong. "A novel core-shell LSCF perovskite structured electrocatalyst with local hetero-interface for solid oxide fuel cells", International Journal of Hydrogen Energy, 2020

Publication

40

E. D. Wachsman, K. T. Lee. "Lowering the Temperature of Solid Oxide Fuel Cells", Science, 2011

Publication

41

Yicheng Zhao, Chun Xia, Lijun Jia, Zhiming Wang, Hongjiao Li, Jinshuai Yu, Yongdan Li. "Recent progress on solid oxide fuel cell: Lowering temperature and utilizing non-

<1%

<1%

<1%

<1%

hydrogen fuels", International Journal of
Hydrogen Energy, 2013

Publication

42

Sune Dalgaard Ebbesen, Søren Højgaard Jensen, Anne Hauch, Mogens Bjerg Mogensen. "High Temperature Electrolysis in Alkaline Cells, Solid Proton Conducting Cells, and Solid Oxide Cells", Chemical Reviews, 2014

Publication

<1%

43

Mahato, Neelima, Amitava Banerjee, Alka Gupta, Shobit Omar, and Kantesh Balani. "Progress in material selection for solid oxide fuel cell technology: A review", Progress in Materials Science, 2015.

Publication

<1%

44

Ahn, J.S.. "High-performance bilayered electrolyte intermediate temperature solid oxide fuel cells", Electrochemistry Communications, 200907

Publication

<1%

45

Yuan Zhang, Ruth Knibbe, Jaka Sunarso, Yijun Zhong, Wei Zhou, Zongping Shao, Zhonghua Zhu. "Recent Progress on Advanced Materials for Solid-Oxide Fuel Cells Operating Below 500 °C", Advanced Materials, 2017

Publication

<1%

46

scholarcommons.sc.edu

<1%

47

Ze-Tian Tao, Yan-Mei Jiang, Libin Lei, Fanglin Chen. "Pr_{0.5}Ba_{0.5}Co_{0.7}Fe_{0.25}Nb_{0.05}O_{3-δ} as air electrode for solid oxide steam electrolysis cells", International Journal of Hydrogen Energy, 2019

Publication

<1%

48

Mingming Li, Jigui Cheng, Yun Gan, Shisong Li, Beibei He, Wenzhou Sun. "Effects of strontium doping on the structure, oxygen nonstoichiometry and electrochemical performance of Pr₂-Sr Ni_{0.6}Cu_{0.4}O_{4+x} (0.1 ≤ x ≤ 0.5) cathode materials", Journal of Power Sources, 2015

Publication

<1%

49

B. Shri Prakash, R. Pavitra, S. Senthil Kumar, S.T. Aruna. "Electrolyte bi-layering strategy to improve the performance of an intermediate temperature solid oxide fuel cell: A review", Journal of Power Sources, 2018

Publication

<1%

50

He, Beibei, Dong Ding, Yihan Ling, Ling Zhao, and Jigui Cheng. "Fabrication and evaluation of stable micro tubular solid oxide fuel cells with BZCY-BZY bi-layer proton conducting electrolytes", International Journal of Hydrogen

<1%

51

163.29.163.133

Internet Source

<1%

52

ecs.confex.com

Internet Source

<1%

53

Xu Chen, Jianqiu Wang, Qingwen Liang, Xi Sun, Xiaofei Zhu, Defeng Zhou, Jian Meng. "Pr₂NiO₄-Pr_{0.2}Ce_{0.8}O_{1.9} composite cathode as a potential cathode material for intermediate temperature solid oxide fuel cells", Solid State Sciences, 2020

Publication

<1%

54

Chang Won Ahn, Euh Duck Jeong, Young Hyeok Kim, Jae Shin Lee, Gwi Sang Chung, Jae Young Lee, Ill Won Kim. "Piezoelectric properties of textured Bi_{3.25}La_{0.75}Ti_{2.97}V_{0.03}O₁₂ ceramics fabricated by reactive templated grain growth method", Journal of Electroceramics, 2008

Publication

<1%

55

Zhang, X.. "Sm_{0.5}Sr_{0.5}CoO₃+Sm_{0.2}Ce_{0.8}O_{1.9} composite cathode for cermet supported thin Sm_{0.2}Ce_{0.8}O_{1.9} electrolyte SOFC operating below 600°C", Journal of Power Sources, 20061006

<1%

56

Lee, K.T..

"Gd_{0.1}Ce_{0.9}O_{1.95}/Er_{0.4}Bi_{1.6}O₃ bilayered electrolytes fabricated by a simple colloidal route using nano-sized Er_{0.4}Bi_{1.6}O₃ powders for high performance low temperature solid oxide fuel cells", Journal of Power Sources, 20120501

Publication

<1%

57

Geng Li, Beibei He, Yihan Ling, Jianmei Xu, Ling Zhao. "Highly active YSB infiltrated LSCF cathode for proton conducting solid oxide fuel cells", International Journal of Hydrogen Energy, 2015

Publication

<1%

58

Shuai He, Qi Zhang, Giulio Maurizio, Lorenzo Catellani, Kongfa Chen, Qibing Chang, Massimo Santarelli, San Ping Jiang. " In Situ Formation of Er Bi O Protective Layer at Cobaltite Cathode/Y O –ZrO Electrolyte Interface under Solid Oxide Fuel Cell Operation Conditions ", ACS Applied Materials & Interfaces, 2018

Publication

<1%

59

research-repository.st-andrews.ac.uk

Internet Source

<1%

60

Mi Young Park, Kwon Deok Seo, Jun-Young Park, Hyung-Tae Lim. "Durability tests of BCY-

<1%

BZY electrolyte fuel cells under severe operating conditions", Journal of Alloys and Compounds, 2018

Publication

61

Hanrui Su, Yun Hang Hu. "Progress in Low-Temperature Solid Oxide Fuel Cells with Hydrocarbon Fuels", Chemical Engineering Journal, 2020

Publication

<1%

62

Emiliana Fabbri, Lei Bi, Daniele Pergolesi, Enrico Traversa. "Towards the Next Generation of Solid Oxide Fuel Cells Operating Below 600 °C with Chemically Stable Proton-Conducting Electrolytes", Advanced Materials, 2012

Publication

<1%

63

Choi, M.-B., K.-T. Lee, H.-S. Yoon, S.-Y. Jeon, E.D. Wachsman, and S.-J. Song. "Electrochemical properties of ceria-based intermediate temperature solid oxide fuel cell using microwave heat-treated $\text{La}_{0.1}\text{Sr}_{0.9}\text{Co}_{0.8}\text{Fe}_{0.2}\text{O}_3$ as a cathode", Journal of Power Sources, 2012.

Publication

<1%

64

S. Giddey, S.P.S. Badwal, A. Kulkarni, C. Munnings. "A comprehensive review of direct carbon fuel cell technology", Progress in Energy and Combustion Science, 2012

Publication

<1%

-
- 65 Thin Film Structures in Energy Applications, 2015. <1%
Publication
-
- 66 H. Güler, F. Kurtuluş. "The synthesis of NiS, ZnS and SrS through solid-gas reaction of sulfidizing gas mixture", Journal of Sulfur Chemistry, 2006 <1%
Publication
-
- 67 Xueli Yao, Ping Li, Baolong Yu, Fei Yang, Jiang Li, Yicheng Zhao, Yongdan Li. "Hydrothermally synthesized NiO-samarium doped ceria nano-composite as an anode material for intermediate-temperature solid oxide fuel cells", International Journal of Hydrogen Energy, 2017 <1%
Publication
-
- 68 Mingfei Liu, Franklin Uba, Ying Liu. "A High-Performance Solid Oxide Fuel Cell with A Layered Electrolyte for Reduced Temperatures", Journal of the American Ceramic Society, 2020 <1%
Publication
-
- 69 Wang, S.F.. "Solid oxide fuel cells with Sm²Ce⁸O₂₂ electrolyte film deposited by novel aerosol deposition method", Journal of Power Sources, 20110601 <1%
Publication
-
- 70 Gang Chen, Wenkang Sun, Yadan Luo, Hailiang Liu, Shujiang Geng, Kai Yu, Guoqiang Liu. <1%

"Investigation of layered Ni 0.8 Co 0.15 Al 0.05 LiO 2 in electrode for low-temperature solid oxide fuel cells", International Journal of Hydrogen Energy, 2018

Publication

71

Gong, Zheng, Wenping Sun, Duo Shan, Yusen Wu, and Wei Liu. "Tuning the thickness of Ba-containing "functional" layer towards high-performance ceria-based solid oxide fuel cells", ACS Applied Materials & Interfaces

Publication

<1%

72

Meigui Xu, Jian Yu, Yufei Song, Ran Ran, Wei Wang, Zongping Shao. "Advances in Ceramic Thin Films Fabricated by Pulsed Laser Deposition for Intermediate-Temperature Solid Oxide Fuel Cells", Energy & Fuels, 2020

Publication

<1%

Exclude quotes On

Exclude matches Off

Exclude bibliography On